

*Contrails*

Cleared January 12th, 1972  
Clearing Authority: Air Force Materials Laboratory

~~AF~~ ML-TR-65-304

**PRECRACKED CHARPY IMPACT FRACTURE  
TOUGHNESS PROPERTIES OF BACKUP FLUX-  
WELDED Ti-5Al-2.5 Sn ALLOY PLATE FROM -320° TO 550°F**

SIDNEY O. DAVIS

AIR FORCE MATERIALS LABORATORY

and

ROGER M. NIEMI

MONSANTO RESEARCH CORPORATION

\*\*\* Export controls have been removed \*\*\*

TECHNICAL REPORT NO. AFML-TR-65-304

JANUARY 1966

AIR FORCE MATERIALS LABORATORY  
RESEARCH AND TECHNOLOGY DIVISION  
~~AF~~ AIR FORCE SYSTEMS COMMAND  
WRIGHT-PATTERSON AIR FORCE BASE, OHIO

This document is subject to special export controls and each transmittal to foreign governments may be made only with prior approval of MAAM, Air Force Materials Laboratory.

## FOREWORD

This report was prepared by Sidney O. Davis of the Materials Information Branch, Materials Applications Division, Air Force Materials Laboratory, Research and Technology Division, Wright-Patterson Air Force Base, Ohio, and Roger M. Niemi of Monsanto Research Corporation, Dayton, Ohio. This program was conducted under Project No. 7381, "Materials Applications," Task 738106, "Design Information Development." The manuscript was released by the authors in August 1965 for publication as an RTD technical report.

This report covers work conducted from February to June 1964.

This technical report has been reviewed and is approved.



D. A. SHINN  
Chief, Materials Information Branch  
Materials Applications Division  
Air Force Materials Laboratory

## ABSTRACT

A program was conducted to evaluate the effects of a proprietary backup flux-welding technique on the impact fracture toughness properties of Ti-5Al-2.5 Sn alloy plate. The flux was the product of Mitron Research and Development Corporation. Precracked Charpy (often called subsize Charpy) specimens were tested under impact loads at  $-320^{\circ}\text{F}$ ,  $-100^{\circ}\text{F}$ , room temperature, and  $550^{\circ}\text{F}$ . The weld and heat affected zone (HAZ) had greater fracture toughness resistance than the base metal. The fracture resistance, work per unit area (W/A) decreased with decreasing test temperature. At  $-320^{\circ}\text{F}$  the weld and HAZ retained 1/3 of their fracture resistance at room temperature. However, the weld- and HAZ-converted W/A impact fracture resistance at  $-320^{\circ}\text{F}$  had a  $K_{IC} \approx 125 \text{ ksi}\sqrt{\text{in.}}$  which indicated good toughness for this temperature. The fracture resistance did not appear to be a function of the specimen's location through the thickness of the plate for a given specimen orientation. In general, the fracture resistance of the weld and HAZ compared to the base metal was excellent.

*Contrails*

## TABLE OF CONTENTS

| SECTION                    | PAGE |
|----------------------------|------|
| I INTRODUCTION             | 1    |
| II PROCEDURE AND MATERIALS | 3    |
| Welding Procedure          | 3    |
| Material                   | 3    |
| Specimens                  | 6    |
| Test Procedure             | 6    |
| III DISCUSSION AND RESULTS | 12   |
| Test Techniques            | 12   |
| Test Results               | 13   |
| IV CONCLUSIONS             | 16   |
| REFERENCES                 | 17   |

## LIST OF ILLUSTRATIONS

| FIGURE |   | PAGE |
|--------|---|------|
| 1.     | Photograph of MITRON Flux Adhering to Back Side of Welded Plates Forming a "Cocoon"                   | 4    |
| 2.     | As-Received Welded Ti-5Al-2.5 Sn Plate  | 4    |
| 3.     | Rockwell "A" Hardness Survey of Weld Metal, Heat Affected Zone, and Base Metal                        | 6    |
| 4.     | Macrograph and Microphotographs of Ti-5Al-2.5 Sn Alloy Plate-Welded with Alloy Wire - No Reverse Pass | 7    |
| 5.     | Subsize Precracked Charpy Test Specimen   | 8    |
| 6.     | Precracked Charpy Specimen Fatigue Machine  | 9    |
| 7.     | Schematic Specimen Cutout Pattern   | 10   |
| 8.     | Charpy Impact Test Machine (24 Ft-Lb Capacity) and 2000°F Furnace                                     | 11   |
| 9.     | Ti-5Al-2.5 Sn Precracked Charpy Fracture Toughness as a Function of Temperature                       | 15   |

## LIST OF TABLES

| TABLE |   | PAGE |
|-------|---|------|
| I.    | Microhardness Surveys of Cross Section of As-Welded Manual TIG Welds With Filler Metal and Automatic TIG Welds Without Filler Metal         | 2    |
| II.   | Transverse As-Welded V-Notch Impact Strength at Room Temperature of 0.050-Inch Ti-6Al-4V Sheet Welds; Welds Ground Flat and Notched in Weld | 2    |
| III.  | Transverse and Longitudinal Weld Tensile Properties of 9/16-Inch Ti-5Al-2.5 Sn Plate Welded With A-110 Wire                                 | 5    |
| IV.   | Tabulated Ti-5Al-2.5 Sn Precracked Charpy Impact Fracture Toughness Test Data   | 14   |

*Contrails*



## SECTION I

### INTRODUCTION

The highly reactive nature of titanium and the corresponding detrimental effect on mechanical properties caused by elements which dissolve interstitially (C, H, O, and N) has plagued fabricators for some time. This problem is acute when welding titanium since the weld and heat affected zones (HAZ) must be protected from contamination. Protection is usually afforded by using an inert cover gas or an inert gas-filled chamber (dry box). With either method, however, the procedure is a costly cumbersome task making on-site welding difficult and often impractical.

Mitron Research and Development Corporation has recently made advances in titanium-welding technology using a backup flux which eliminates reverse-side shielding. This flux can be applied as a paste, powder, or tape which fuses upon heating and subsequently volatilizes to seal the weld from the atmosphere.

The development described was sponsored by the Navy as a technique for welding Ti plate. Further development in applying the technique to sheet material was conducted by the Air Force under Contract AF 33 (615)-1384.

The initial report issued by Mitron Research and Development Corporation on the development of nonreactive fluxes for use when welding titanium has been released under Contract AF 33 (615)-1384 (References 1 and 2). Promising results have been obtained utilizing fluxes as a backup for gas tungsten arc-welding of 0.050-inch-thick Ti-6Al-4V. To date, paste fluxes appear better than powder fluxes because of residual moisture in the powder. This is partially shown in Table I by the lower as-welded hardness. Table II shows the conventional impact properties of the welds which were made (Reference 1). The flux compositions were not revealed. The fluxes were sufficiently coherent after one pass to permit multipass welding and could be removed with water and a wire brush (Reference 1).

This TR reports in-house work done to determine the fracture resistance characteristics of one of the titanium plates welded by Mitron. The fracture resistance measures the ability of a material to resist crack propagation when flaws are present in the material. This support work was done at the request of the Advanced Fabrication Techniques Branch, Manufacturing Technology Division, Air Force Materials Laboratory. In the ensuing report little emphasis is placed on welding procedures and the actual use of the flux. This type of information is beyond the scope of this report, but is available to interested readers by obtaining Mitron's report (Reference 3). The fracture resistance of the weld, HAZ, and base metal was evaluated using the precracked Charpy Test Method developed by Manlabs, Incorporated (References 4 and 5).

TABLE I

Microhardness Surveys of Cross Section of As-Welded  
Manual Tig Welds With Filler Metal and Automatic Tig  
Welds Without Filler Metal \*

| Welding<br>Technique | Filler        | Average Hardness, $R_c$ |      |      | Flux Form            |
|----------------------|---------------|-------------------------|------|------|----------------------|
|                      |               | Base                    | HAZ  | Weld |                      |
| Manual TIG           | Ti-6Al-4V     | 33.1                    | 38.0 | 38.3 | Powdered             |
|                      | Ti-5Al-2.5 Sn | 34.0                    | 38.7 | 40.8 | "                    |
|                      | Ti-5Al-2.5 Sn | 32.5                    | 37.0 | 38.0 | "                    |
|                      | CP-Ti         | 35.0                    | 37.0 | 38.0 | "                    |
| Automatic TIG        | None          | 34.6                    | 36.9 | 41.0 | Powdered             |
|                      | None          | 33.1                    | 36.0 | 37.0 | Paste                |
|                      | None          | 36.7                    | 36.7 | 39.0 | Paste                |
|                      | None          | 35.8                    | 36.6 | 36.2 | None (gas<br>backup) |

\* See Reference 1

TABLE II

Transverse As-Welded V-Notch Impact Strength at Room  
Temperature of 0.050-Inch Ti-6Al-4V Sheet Welds;  
Welds Ground Flat and Notched in Weld \*

| Material           | Average Impact Strength,<br>Inch-Pounds |
|--------------------|---|
| Base material      | 22.8                                    |
| Argon backup       | 20.1                                    |
| Powder-flux backup | 10.6                                    |
| Paste-flux backup  | 20.2                                    |

\* See Reference 1

## SECTION II

### PROCEDURE AND MATERIALS

#### WELDING PROCEDURE

The Ti-5Al-2.5 Sn plate was MIG welded using A-110-AT\* filler wire with fore and aft argon shielding. The halide-chloride flux was applied to the reverse side of the plate and fused to form a "cocoon" as shown in Figure 1. The weld joint was a 60° Vee butt weld without a reverse-side weld pass. Four passes were required to fill the joint on a 9/16-inch-thick plate. Normal cleaning and MIG welding procedures were used.

#### MATERIAL

The comparative chemical composition of parent material and weld wire (Reference 3) is as follows:

| ELEMENT         | C     | O          | H<br>(PPM) | N     | Fe   | Cl    | Na    | K     | Al   | Sn   | Mn    | Ti  |
|-----------------|-------|------------|------------|-------|------|-------|-------|-------|------|------|-------|-----|
| PARENT<br>MAT'L | 0.030 | 0.096      | 76-83      | 0.01  | 0.14 | 0.024 | 0.006 | 0.001 | 5.50 | 2.50 | 0.030 | BAL |
| WELD WIRE       | 0.034 | 0.07-0.092 | 37-61      | 0.012 | 0.21 | —     | —     | —     | 5.56 | 2.49 | 0.014 | BAL |

The as-received welded Ti-5Al-2.5 Sn plate is shown in Figure 2. Nominal dimensions were 12 inch by 6 inch by 9/16 inch. This plate was received from the mill in the forged and vacuum-annealed condition. Typical mechanical properties are listed in Table III (Reference 3). Hardness measurements revealed little variation across the weld and HAZ. This consistency, shown in Figure 3, indicates a minimal amount of interstitial pickup in the weldment.

Metallographic examination of a companion plate welded in the same manner as the one tested revealed the sequenced macro and micro photographs shown in Figure 4 (Reference 3).

---

\* A-110-AT is a crucible designation for Ti-5Al-2.5 Sn.



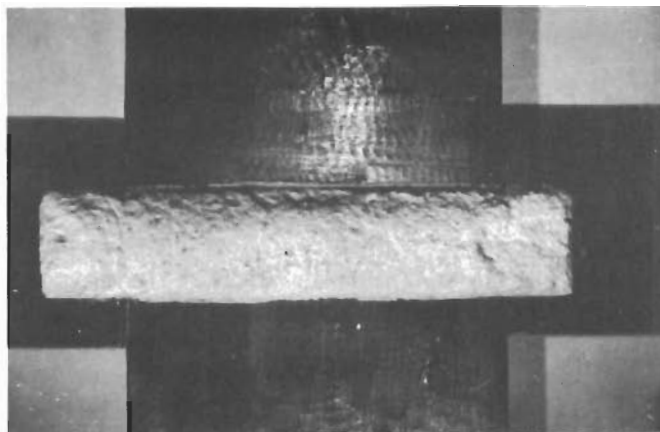


Figure 1. Photograph of MITRON Flux Adhering to Back Side of Welded Plates Forming a "Cocoon"

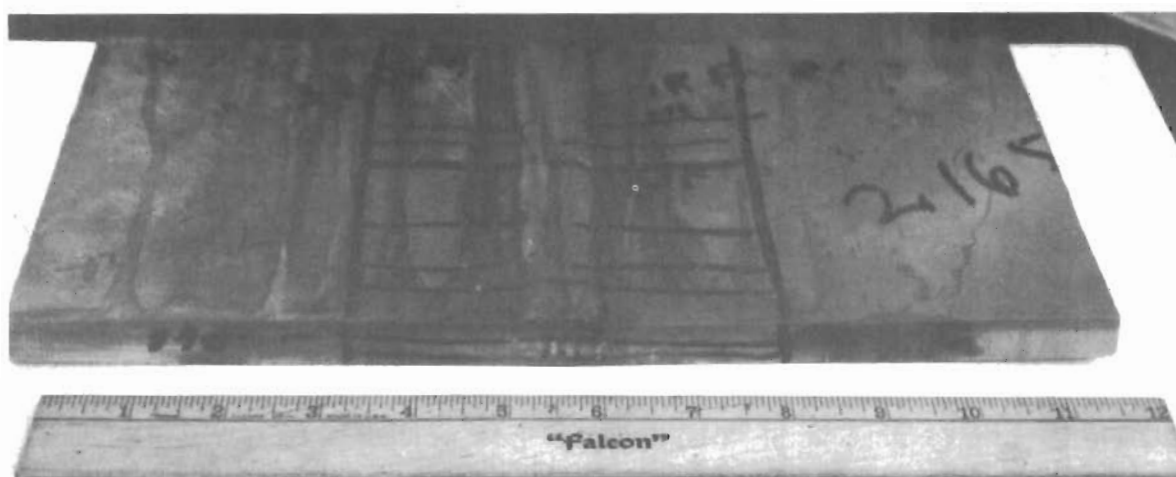

TOP

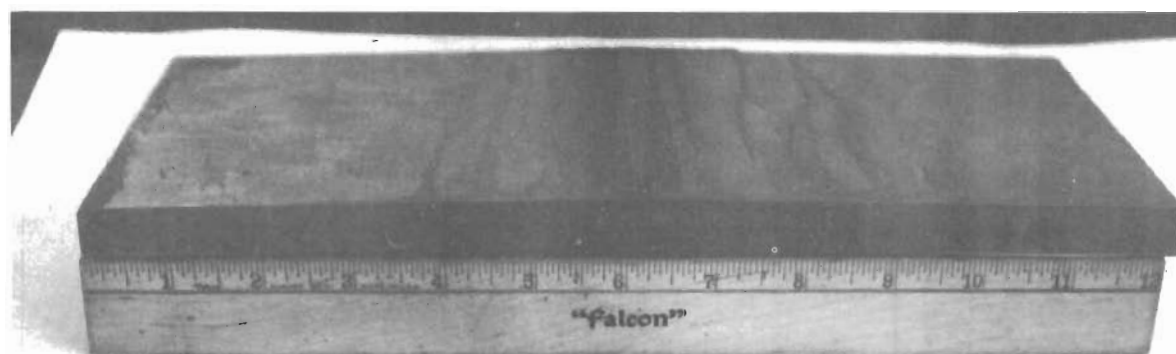

BOTTOM

Figure 2. As-Received Welded Ti-5Al-2.5 Sn Plate

Contrails

TABLE III


Transverse and Longitudinal Weld Tensile Properties of 9/16-Inch  
Ti-5Al-2.5 Sn Plate Welded With A-110 Wire\*

| Specimen Type<br>Cut From Plate | Y. S.   | T. S.   | % Elong. **<br>in 2 inches | % Elong.<br>in 1 Inch | Fracture<br>Location | Remarks                           |
|---------------------------------|---------|---------|----------------------------|-----------------------|----------------------|-----------------------------------|
| .357 Round (trans.)             | 113,500 | 126,000 | 11.5                       | ----                  | weld                 | Good gas coverage and flux backup |
| Full Size                       | 111,000 | 125,000 | 7.0                        | 14.0                  | weld                 | " " " " "                         |
| Full Size                       | 112,000 | 126,000 | 8.5                        | 17.0                  | weld                 | " " " " "                         |
| Full Size                       | 108,000 | 122,000 | 9.9                        | 19.8                  | weld                 | Good gas coverage and back pass   |
| Full Size                       | 112,000 | 125,000 | 8.5                        | 17.0                  | weld                 | " " " " "                         |
| .357 Round                      | 113,500 | 120,500 | 8.0                        | ----                  | weld                 | " " " " "                         |
| .357 Round                      | 120,000 | 129,000 | 20.0                       | ----                  | ----                 | Parent material                   |
| .357 Round                      | 116,500 | 122,500 | 16.4                       | ----                  | ----                 | " "                               |
| Full Size                       | 111,000 | 127,500 | 7.5                        | 15.0                  | ----                 | Good gas coverage and flux backup |
| .357 Round (long.)              | 109,000 | 117,500 | 11.0                       | ----                  | ----                 | All-weld tensile specimen         |
| .357                            | 121,000 | 128,000 | 17.0                       | ----                  | ----                 | HAZ specimen                      |
| .357 Round                      | 126,000 | 132,000 | 17.0                       | ----                  | ----                 | Heat affected zone specimen       |

\*See Reference 3

\*\* The % elongation is presented for 2-inch and 1-inch gage lengths for the full-size tensile bars. This was done because the total amount of actual elongation occurring during testing was well within a 1-inch gage length, though a 2-inch gage length was used. Based on this fact it is felt that the % elongation for the 1-inch gage length is more realistic than the data presented for the 2-inch gage length.



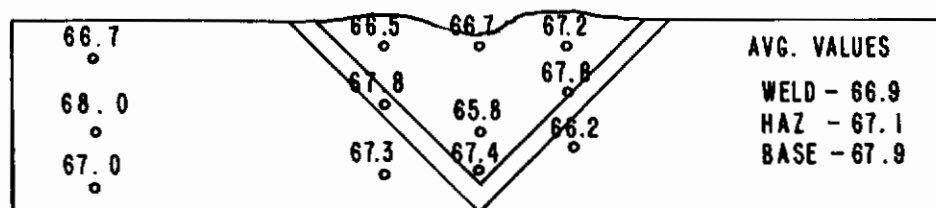

Note: Ti-5Al-2.5 Sn welded with A-110-AT wire; no reverse weld pass. See, also, Reference 3.

Figure 3. Rockwell "A" Hardness Survey of Weld Metal, Heat Affected Zone, and Base Metal (Reference 3)

## SPECIMENS

Fracture resistance of the weld, HAZ, and base metal was evaluated using the precracked Charpy specimen shown in Figure 5. Note that Charpy dimensions are standard except for a reduced thickness. A short crack ( $\approx 1/8$  inch in length) was fatigued at the tip of the Vee notch into the specimens to simulate service cracks prior to precracked Charpy testing with the machine shown in Figure 6 manufactured by Manlabs, Incorporated.

The specimens were removed and prepared from the Ti plate using the following procedure:


1. Cut into sections representing the weld, base metal, and HAZ using a Norton No. 32A-46-F12-VBP wheel.
2. Surface grind the thickness to  $1/8$  inch and the height to 0.394 inch.
3. Macro etch to locate weld and HAZ.
4. Notch and trim excess length (from 3.5 to 2.165 inch).
5. Surface grind the thickness to 0.100 inch.
6. Fatigue crack to a total depth of  $\approx 0.125$  inch.

The cutout pattern used was designed to yield the maximum number of specimens allowing tests in two crack-propagation directions (see Figure 7). A total of 59 specimens were prepared in this manner.


## TEST PROCEDURE

The precracked Charpy (often called subsize Charpy) specimens were tested at  $-320^{\circ}\text{F}$ ,  $-100^{\circ}\text{F}$ , room temperature, and  $550^{\circ}\text{F}$ . Subzero tests were accomplished by rapid transfer of the specimen from the environment to the impact tester anvil. Elevated temperatures were monitored with Cr-Al thermocouples located in the furnace shown in Figure 8. Testing was done on the 24 ft-lb capacity impact machine also shown in Figure 8. The machine was developed and designed for subsize Charpy testing by Manlab Incorporated. Test values are reported as work/area (W/A) and may be related to the fracture toughness  $K_{IC}$  by the formula  $K_{IC}^2 \approx EG_C$  where W/A is substituted for  $G_C$  and E is the elastic modulus. The reader is cautioned that  $W/A \approx G_C$  is true only on a unit basis, (both  $\frac{\text{in-lb}}{\text{in}^2}$ ). From a fundamental conceptual viewpoint, the parameters W/A and  $G_C$  are different.


After testing, the fractured surface (not the fatigue-cracked surface) area A, was measured with a 50X toolmakers microscope to an accuracy of  $\pm 0.001 \text{ inch}^2$  for the calculation of W/A impact toughness values of Ti-5Al-2.5 Sn Alloy.

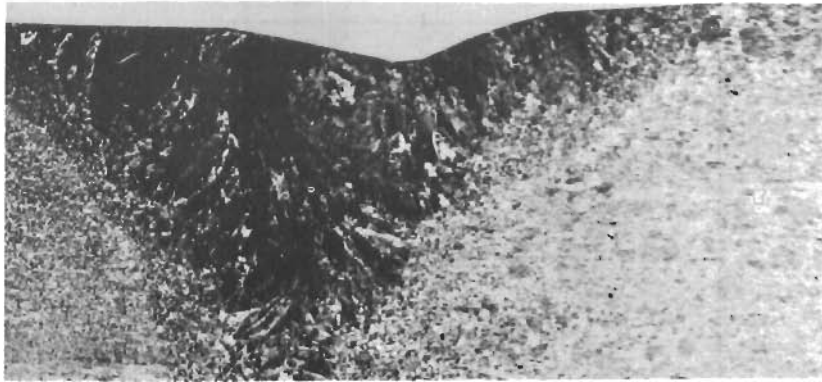

4a. Macrograph of Welded Specimen Etchant:  
Modified Kroll's Etch, Magnification: 4X

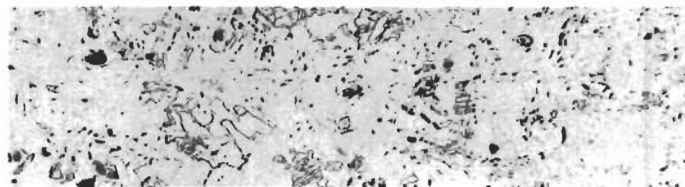

4b. Micrograph of Base Material Etchant:  
Modified Kroll's Etch, Magnification: 100X

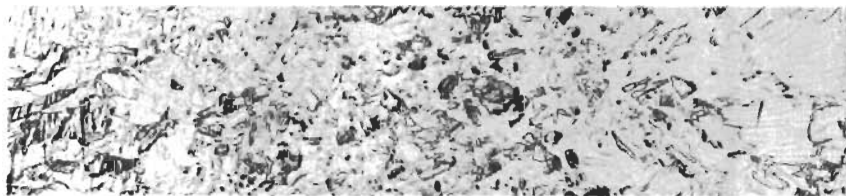

4c. Micrograph of Heat Affected Zone Etchant:  
Modified Kroll's Etch, Magnification: 100X



4d. Micrograph of Fusion Zone Etchant:  
Modified Kroll's Etch, Magnification: 100X

Figure 4. Macrograph and Microphotographs of Ti-5Al-2.5 Sn Alloy Plate-Welded With Alloy Wire. No Reverse Pass.  
(See Reference 3.)

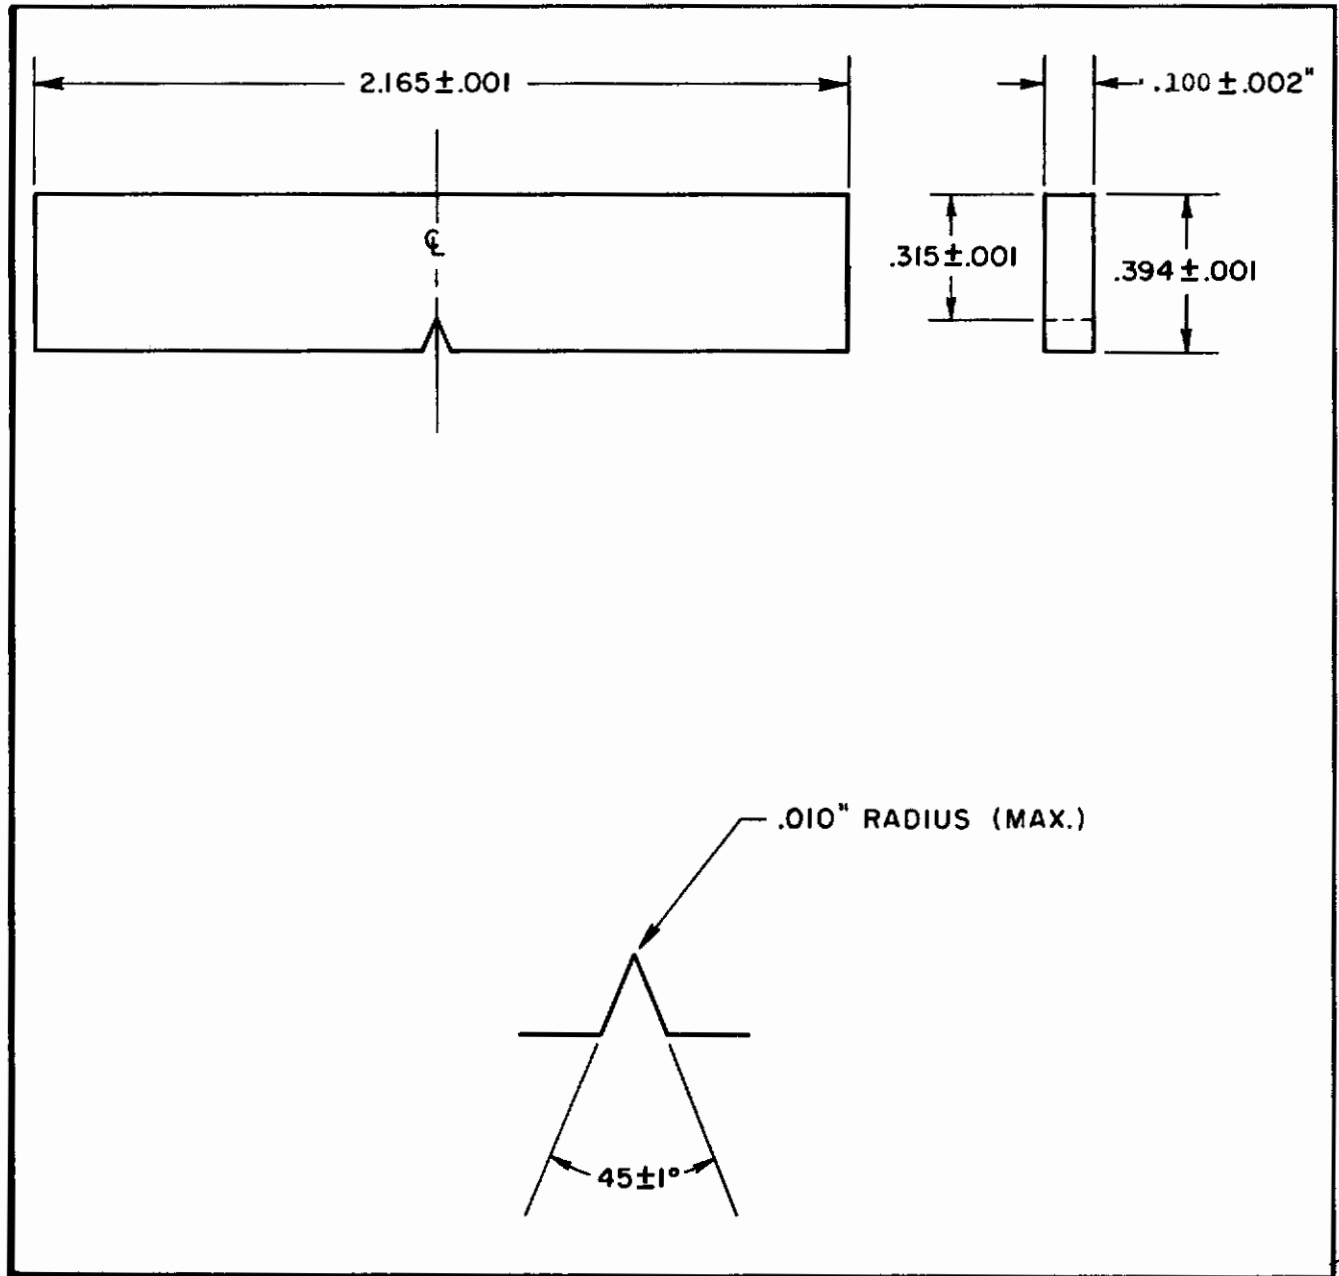


Figure 5. Subsize Precracked Charpy Test Specimen



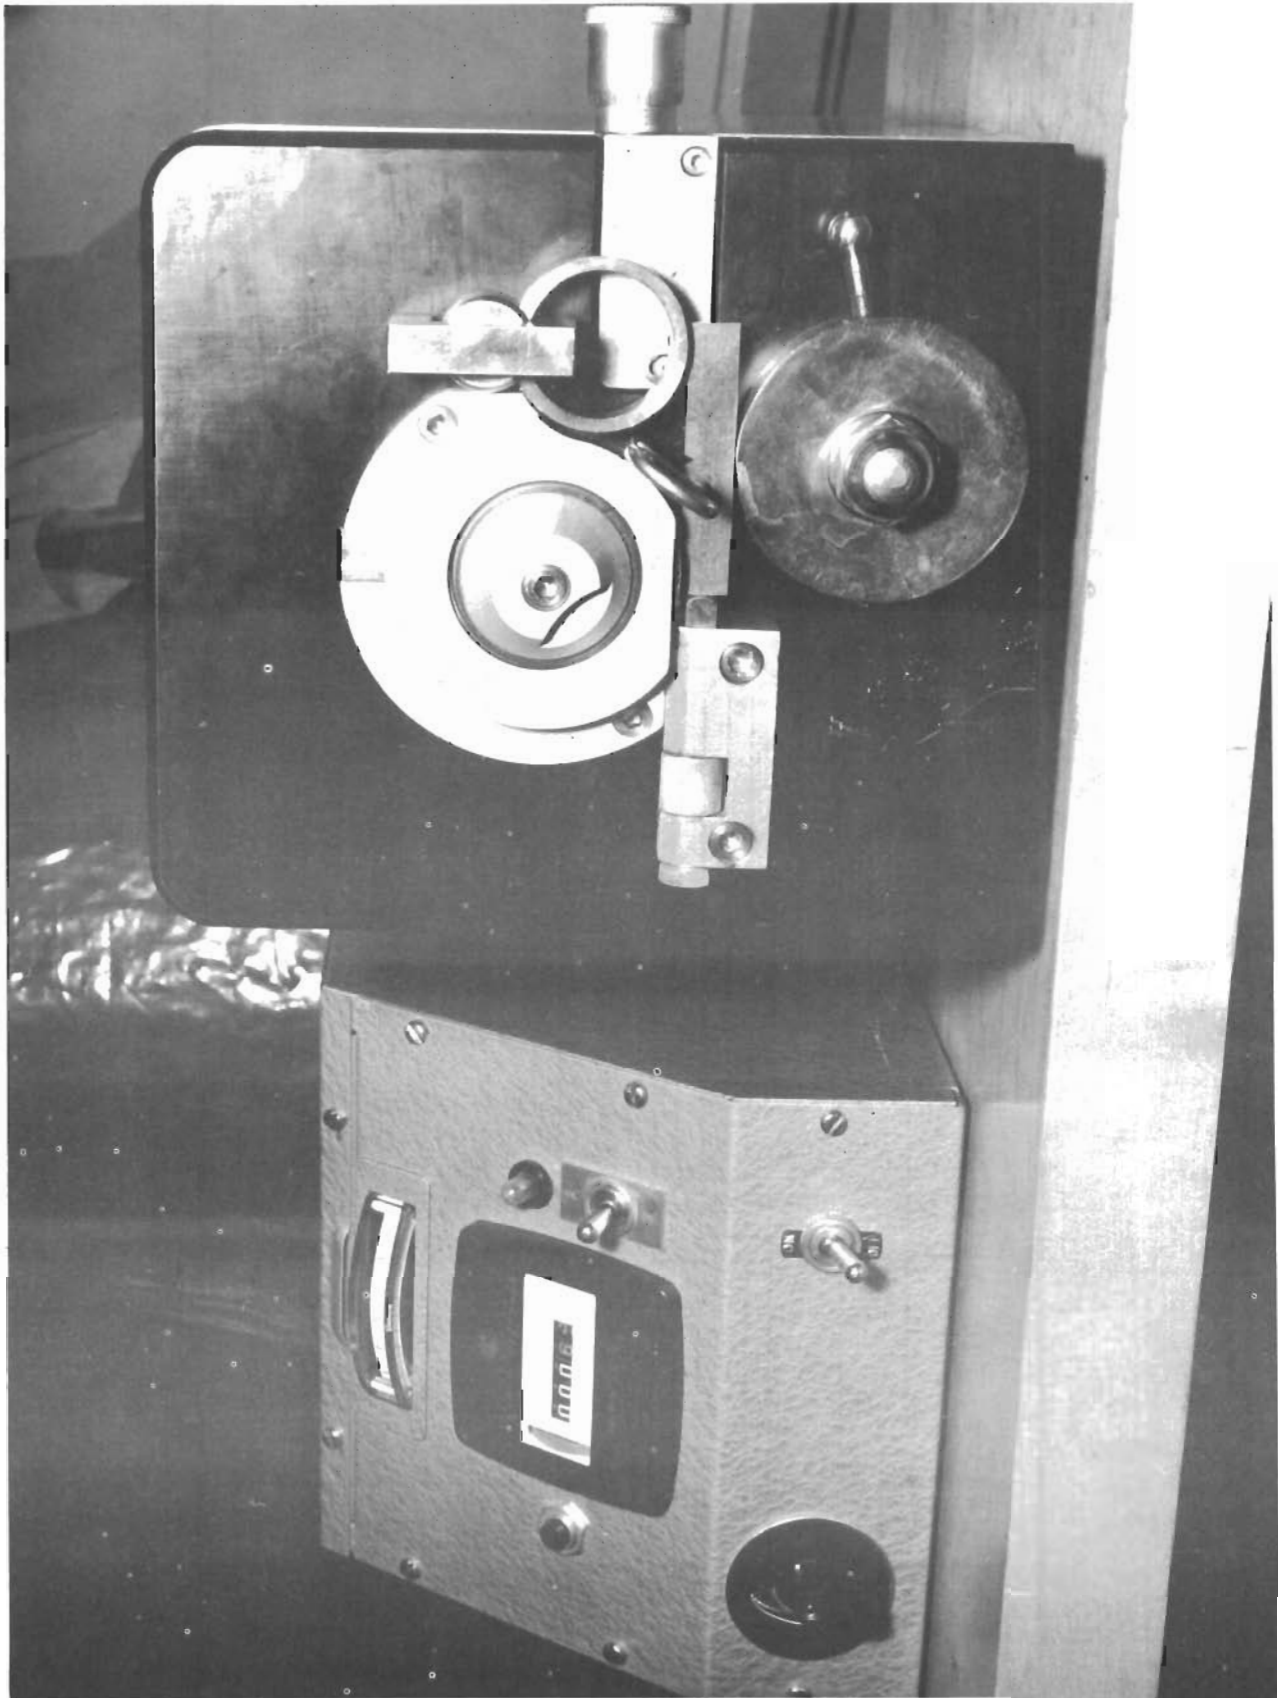


Figure 6. Pre-cracked Charpy Specimens Fatigue Machine

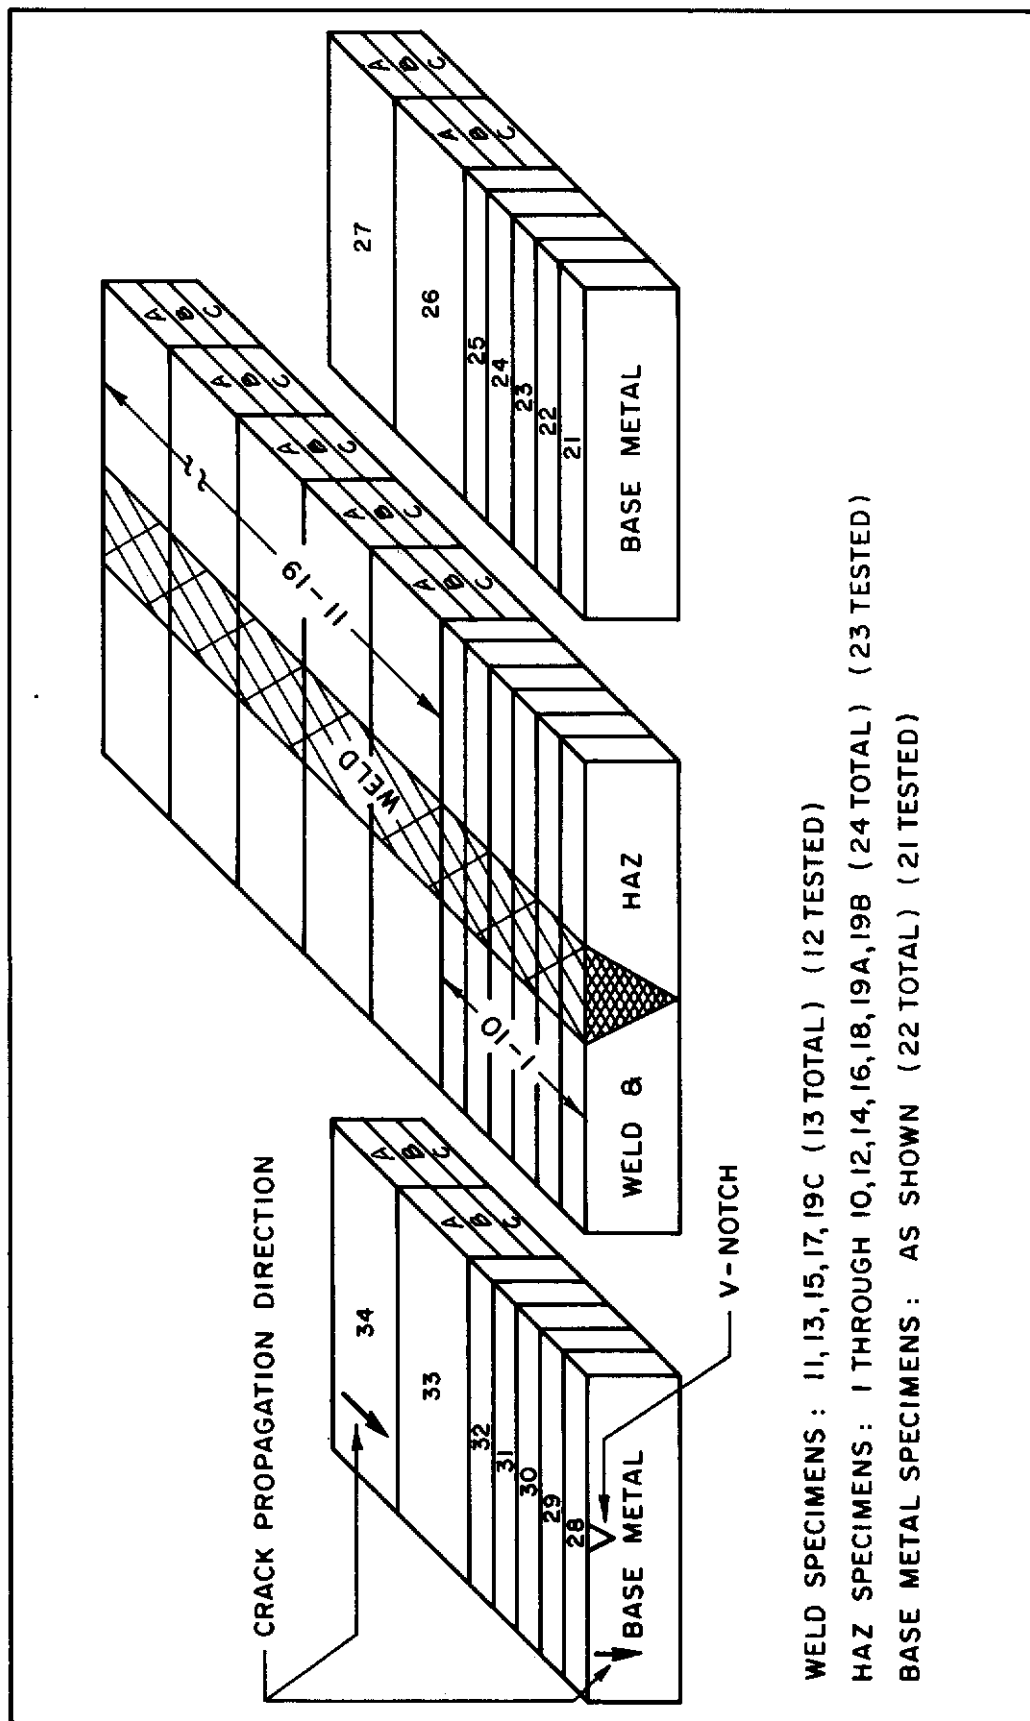


Figure 7. Schematic Specimen Cutout Pattern

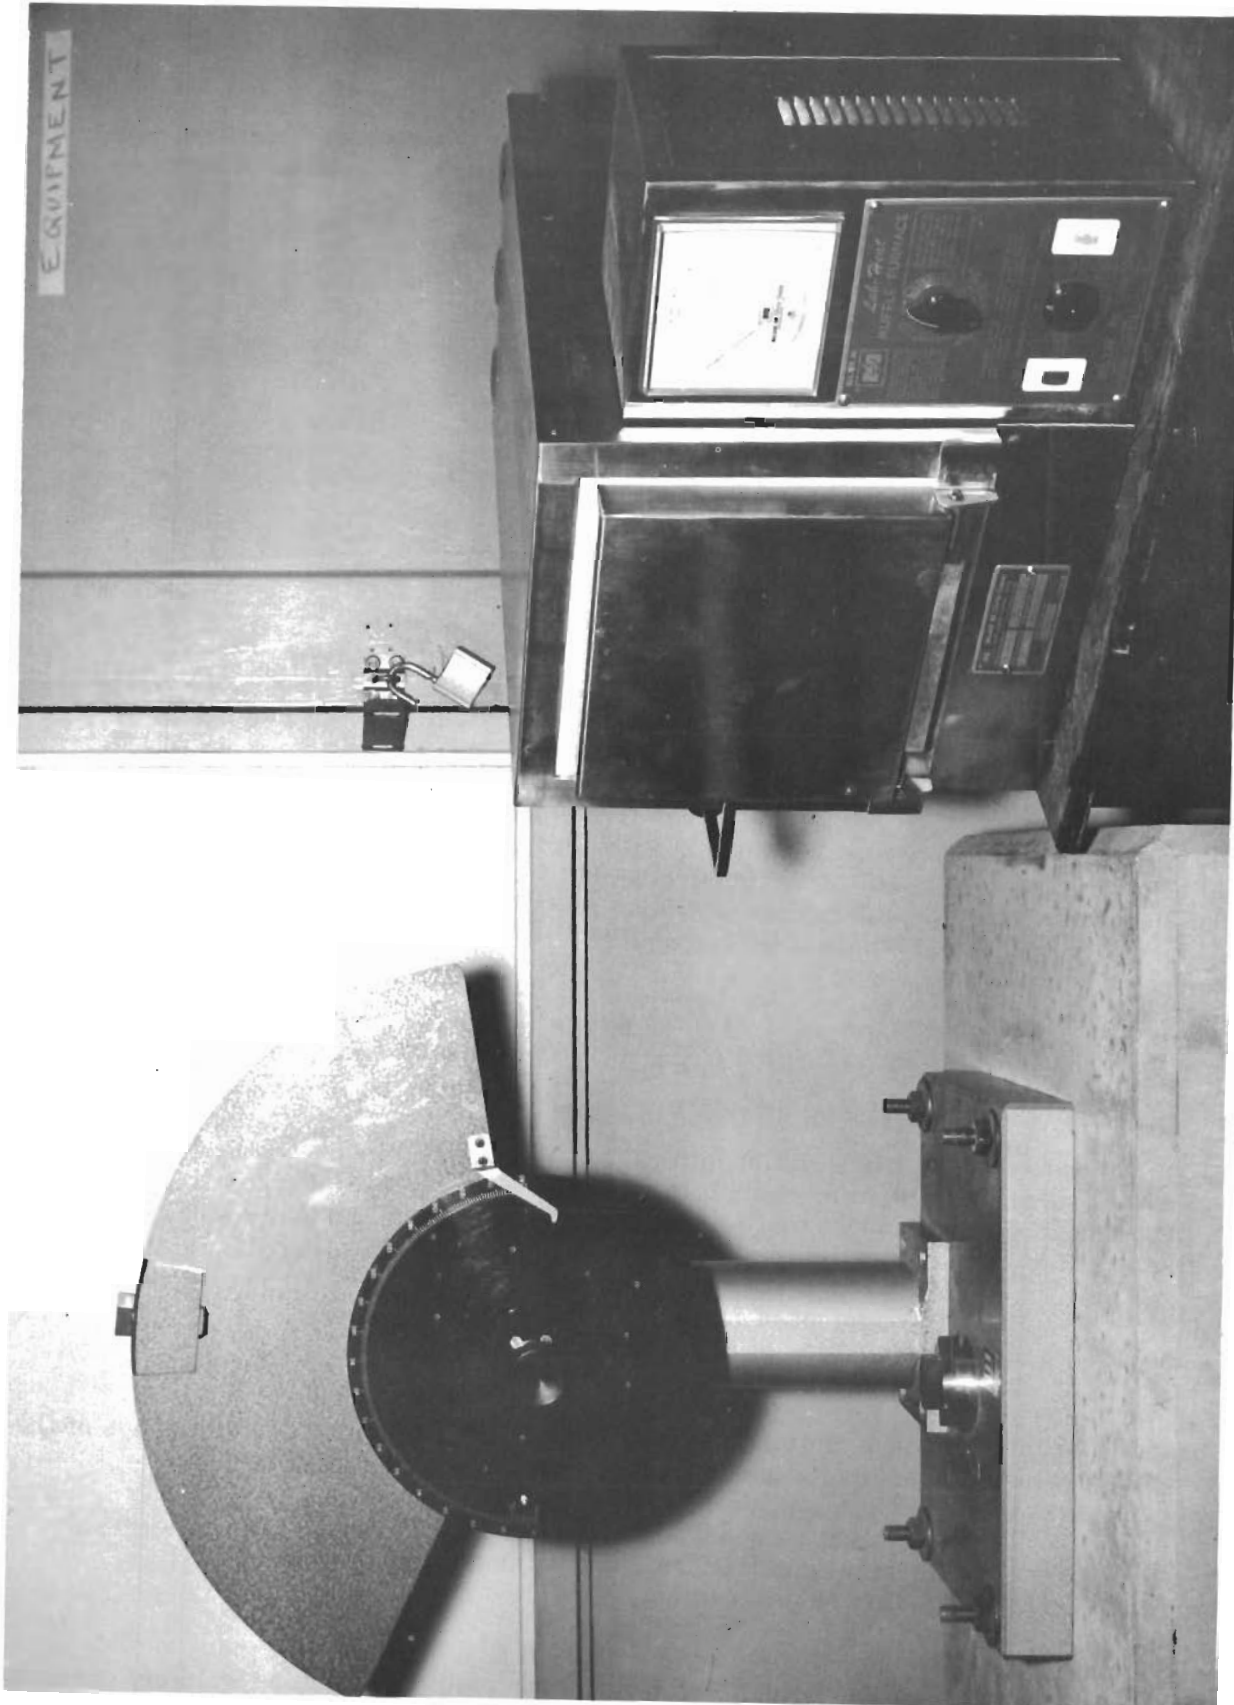


Figure 8. Charpy Impact Test Machine (24 Ft-Lb Capacity) and 2000°F Furnace.

## SECTION III

### DISCUSSION AND RESULTS

#### TESTING TECHNIQUE

Currently, there is a correlation between  $G_C$  and  $W/A$  (under slow bend loading only) based on the prediction of residual strength ( $\sigma$ ) using the following modified Griffith-Orowan relationship used by Hartbower (References 4 and 5).

$$\sigma = \sqrt{\frac{\left(\frac{W}{A}\right) E}{\pi a_0}} \approx \sqrt{\frac{G_C E}{\pi a_0}}$$

where:

- $E$  = Young's modulus
- $a_0$  = initial critical half-crack length
- $W/A$  = work done on the specimen per unit area or energy absorbed by the material per unit area
- $G_C$  = the energy release rate under plane stress conditions
- $\sigma$  = the residual strength (crack strength). It is the impaired or reduced ultimate strength of a member containing a crack, notch, or some form of physical material damage.

Manlabs, Incorporated, has reported a relative good agreement (15%) between the  $G_C$  and  $W/A$  values in terms of the residual strength ( $\sigma$ ) of four medium carbon steels (Reference 4). The measured values of residual strength were based on center-notched tensile tests. The predicted values were based on slow bend ( $W/A$ ) test values and use of the modified Griffith-Orowan mathematical relation (Reference 4):

$$\sigma = \sqrt{\frac{\left(\frac{W}{A}\right) E}{\pi a_0}}$$

It should be cautioned that this relationship is based upon tensile-testing strain rates and not impact strain rates as utilized to evaluate the Ti-5Al-2.5 Sn welded alloy in this program. However, precracked Charpy impact test for determining fracture resistance is advantageous from the standpoint of economy with respect to:

1. The amount of material used for testing
2. Preparation of test specimens
3. Testing time

Also, based upon a common specimen geometry and testing conditions the influence of the following can be evaluated expediently under Charpy impact fracture testing:

1. Chemical composition
2. Thermal and mechanical treatment
3. Quality of processing
4. Melting practice
5. Temperature effects
6. Quality control of processing methods, such as welding, casting, rolling, forging, and extruding

**TEST RESULTS**

The data obtained is presented in Table IV and is graphed in Figure 9. If the weld had absorbed interstitial elements, the fracture tests would have revealed a lower fracture resistance in the weld and HAZ compared to the base metal. In fact, 0.5%  $O_2$  will render Ti uselessly brittle. But, it is obvious from Figure 9 that the weld and HAZ had greater fracture resistance than the base metal. As expected, the fracture resistance (W/A) decreased with decreasing test temperature. But, compared to room temperature W/A values, at  $-320^\circ F$  the weld and HAZ retained 1/3 of their fracture resistance with a converted  $K_{IC} \approx 125 \text{ ksi} \sqrt{\text{in.}}$  indicating good toughness under this severe condition.

Fracture resistance did not appear to be a function of the specimen's location in the plate, i.e., in positions A, B, or C (Figure 7). Weld specimens were tested only in one direction since it was assumed there would be no directional effects in the weld metal.

Mitron has reported the following nominal transverse tensile weld properties for the material tested:

|                    |                 |
|--------------------|-----------------|
| 0.2 per cent Y. S. | - 112 ksi       |
| T. S.              | - 126 ksi       |
| Elongation         | - 7-11 per cent |



*Contrails*

TABLE IV

Tabulated Ti-5Al-2.5Sn Precracked  
Charpy Impact Fracture Toughness  
Test Data

|          | Room Temperatures |              |              | 550°F                           |      |      |
|----------|-------------------|--------------|--------------|---------------------------------|------|------|
|          | BM                | Weld         | HAZ          | BM                              | Weld | HAZ  |
| Normal   | 2050*             | -            | 2900         | 3350                            | -    | 2600 |
|          | 2375              | -            | 2950         | 3575                            | -    | 3775 |
|          | 1750              | -            | 2175         | 3725                            | -    | 3700 |
| Avg.     | 2060              |              | 2675         | 3550                            |      | 3360 |
| Parallel | 1375              | 2900         | 2350         | 3200                            | 3875 | 3500 |
|          | 1775              | 3300         | 2500         | 2750                            | 4200 | 3025 |
|          | 1625              | 2475         | 2025         | 3250                            | 3650 | 3400 |
| Avg.     | 1600              | 3100<br>2900 | 2425<br>2290 | 3100                            | 3900 | 3310 |
|          | -100°F            |              |              | -320°F (Liquid N <sub>2</sub> ) |      |      |
|          | BM                | Weld         | HAZ          | BM                              | Weld | HAZ  |
| Normal   | 1275              | -            | 2075         | 575                             | -    | 1050 |
|          | 1225              | -            | 1800         | 500                             | -    | 825  |
|          | -                 | -            | -            | -                               | -    | -    |
| Avg.     | 1250              |              | 1940         | 540                             |      | 940  |
| Parallel | 1200              | 2300         | 1775         | 800                             | 750  | 700  |
|          | 1225              | 2575         | 1975         | 600                             | 925  | 750  |
|          | -                 | 2400         | 1825         | 500                             | 1075 | 750  |
| Avg.     | 1210              | 2425         | 1860         | 630                             | 920  | 710  |

\* W/A values in  $\frac{\text{in.} \cdot \text{lbs}}{\text{in.}^2}$

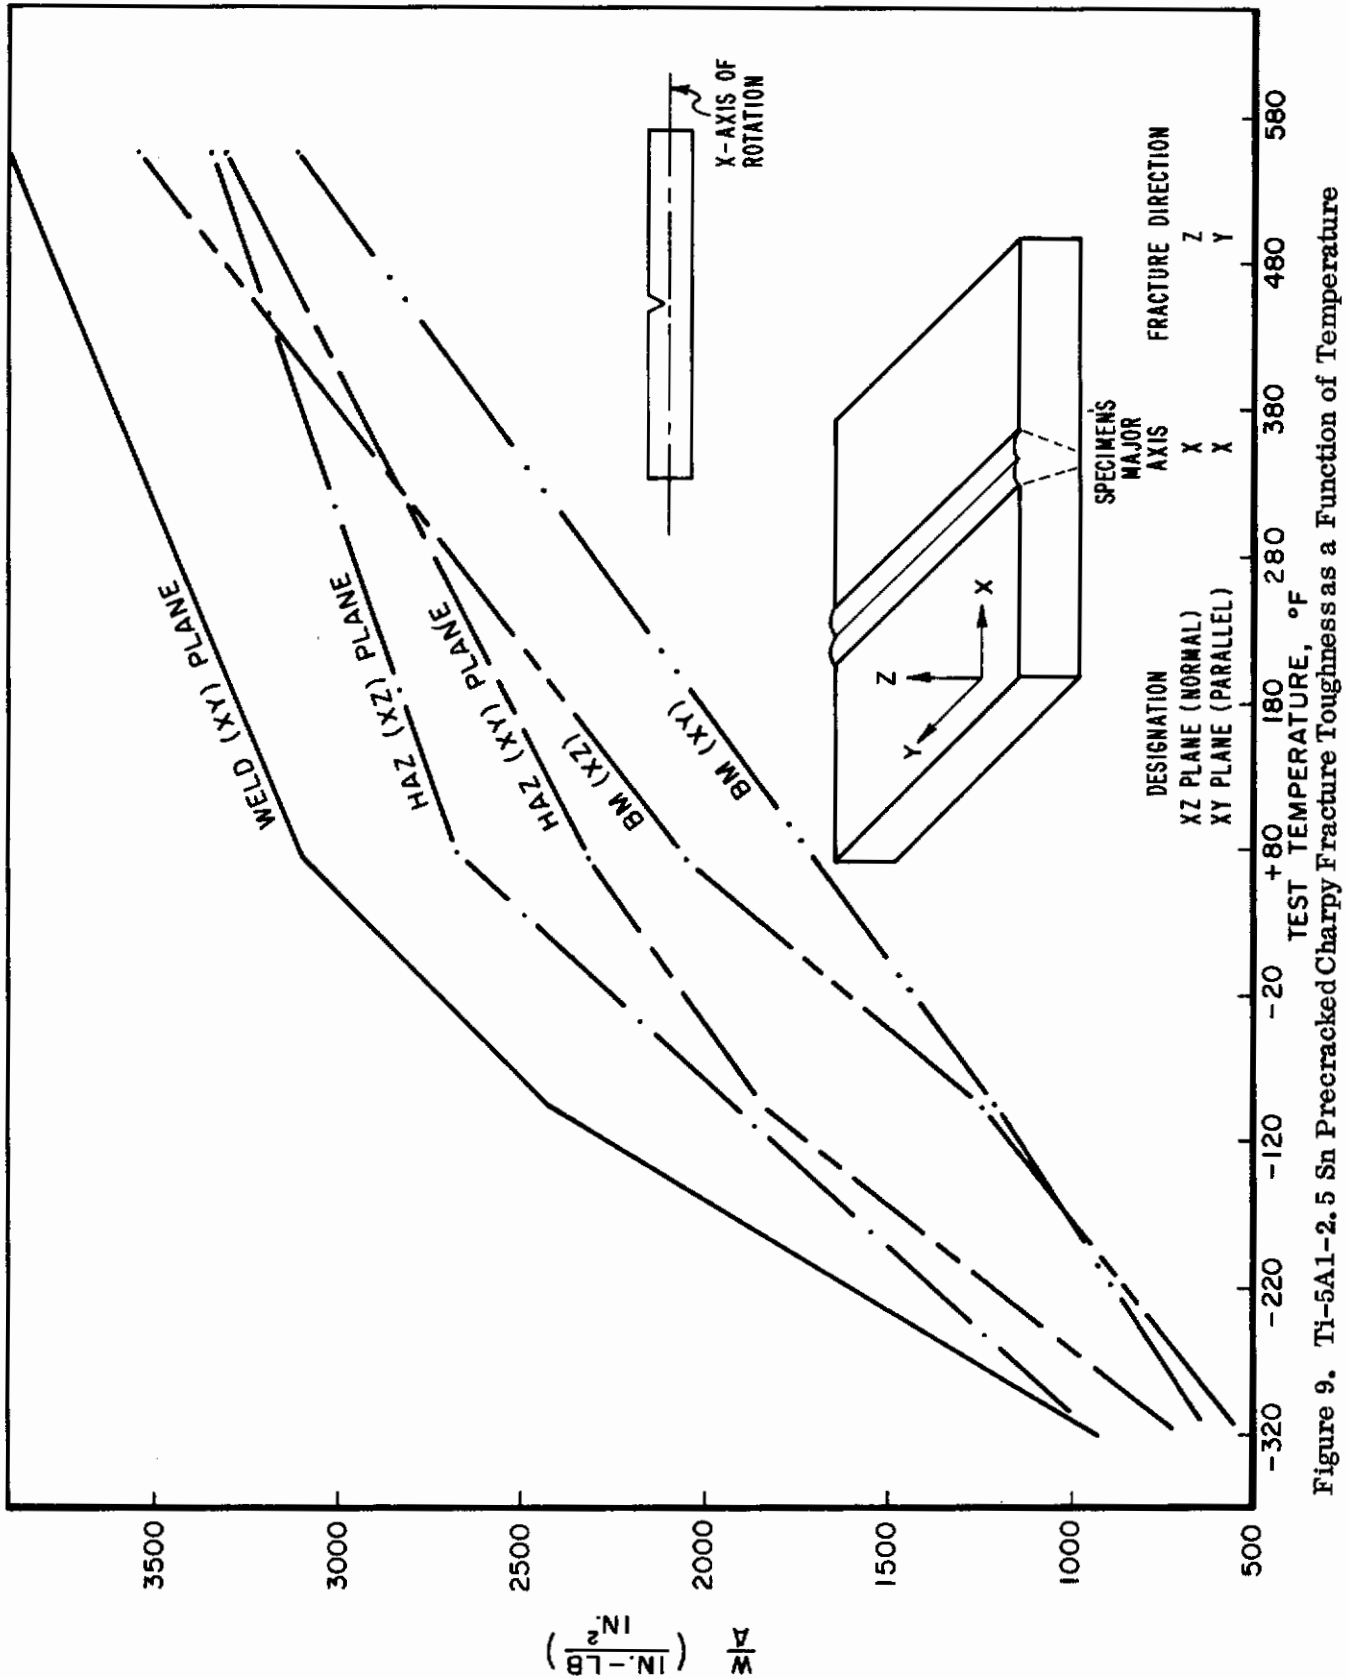


Figure 9. Ti-5Al-2.5 Sn Precracked Charpy Fracture Toughness as a Function of Temperature

## CONCLUSIONS

On the basis of fracture resistance, Mitron's backup flux-welding technique is promising. In general, the fracture resistance of the weld and HAZ compared to the base metal was excellent.

The precracked Charpy impact testing technique demonstrated that it is advantageous from the standpoint of accuracy, reproducibility, and economy with respect to: (1) the amount of material used for testing, (2) preparation of test specimens, and (3) testing time required to evaluate the welding technique. However, the technique cannot be used to obtain data to calculate accurate  $K_{IC}$ 's and critical flaw sizes of high strength materials under plane stress or plane strain conditions for design use.

The precracked Charpy testing technique does, however, have merit when evaluating the influence of chemistry, heat treatment, processing history, joining techniques, and quality control on the mechanical properties of metallic materials.



## REFERENCES

1. R. M. Evans, Metal Joining, DMIC Review of Recent Developments, Battelle Memorial Institute, Columbus 1, Ohio, August 28, 1964.
2. Mitron Research and Development Corporation, Tungsten Inert Gas Arc Welding Titanium Using a Nonreactive Flux, Interim Engineering Progress Report, May 1964.
3. Mitron Research and Development Corporation, Application of Mitron's Nonreactive Flux in Welding MST-40 Titanium and Ti-5Al-2.5 Sn Plate, Final Report, June 1963.
4. C. E. Hartbower and G. M. Orner, Manlabs, Incorporated, Investigation of Fracture Toughness in High Strength Alloys, ASD-TDR-62-868, Part II, Aeronautical Systems Division, Wright-Patterson AFB, Ohio, January 1964.
5. C. E. Hartbower and G. M. Orner, Manlabs, Incorporated, Metallurgical Variables Affecting Fracture Toughness In High Strength Sheet Alloys, ASD-TDR-62-868, Part I, October 1962.

*Contrails*

Unclassified

Security Classification

| DOCUMENT CONTROL DATA - R&D  |  |                             |
|--|--|-----------------------------|
| (Security classification of title, body of abstract and indexing annotation must be entered when the overall report is classified)   |  |                             |
| <b>1. ORIGINATING ACTIVITY (Corporate author)</b><br>Materials Information Branch<br>Materials Applications Division<br>Air Force Materials Laboratory   | <b>2a. REPORT SECURITY CLASSIFICATION</b><br>Unclassified<br><hr/> <b>2b. GROUP</b>  |                             |
| <b>3. REPORT TITLE</b><br>Precracked Charpy Impact Fracture Toughness Properties of Backup Flux-Welded Ti-5Al-2.5 Sn Alloy Plate from -320° to 550°F   |  |                             |
| <b>4. DESCRIPTIVE NOTES (Type of report and inclusive dates)</b><br>Final Report. February to June 1964  |  |                             |
| <b>5. AUTHOR(S) (Last name, first name, initial)</b><br>Davis, Sidney O.<br>Niemi, Roger M.  |  |                             |
| <b>6. REPORT DATE</b>  | <b>7a. TOTAL NO. OF PAGES</b><br>26  | <b>7b. NO. OF REFS</b><br>5 |
| <b>8a. CONTRACT OR GRANT NO.</b><br><br><b>b. PROJECT NO.</b> 7381, Task 738106<br><br><b>c.</b><br><br><b>d.</b>  | <b>9a. ORIGINATOR'S REPORT NUMBER(S)</b><br>AFML-TR-65-304<br><hr/> <b>9b. OTHER REPORT NO(S) (Any other numbers that may be assigned this report)</b> |                             |
| <b>10. AVAILABILITY/LIMITATION NOTICES</b><br>Qualified users may obtain copies of this report from the Defense Documentation Center. Release to CFSTI is not authorized.  |  |                             |
| <b>11. SUPPLEMENTARY NOTES</b>   | <b>12. SPONSORING MILITARY ACTIVITY</b><br>Research and Technology Division<br>Air Force Systems Command<br>Wright-Patterson Air Force Base, Ohio      |                             |
| <b>13. ABSTRACT</b><br>A program was conducted to evaluate the effects of a proprietary backup flux-welding technique on the impact fracture toughness properties of Ti-5Al-2.5 Sn alloy plate. The flux was the product of Mitron Research and Development Corporation. Precracked Charpy (often called subsize Charpy) specimens were tested under impact loads at -320°F, -100°F, room temperature, and 550°F. The weld and heat affected zone (HAZ) had greater fracture toughness resistance than the base metal. The fracture resistance work per unit area (W/A) decreased with decreasing test temperature. At -320°F the weld and HAZ retained 1/3 of their fracture resistance at room temperature. However, the weld- and HAZ-converted W/A impact fracture resistance at -320°F had a $K_{IC} \approx 125 \text{ ksi } \sqrt{\text{in.}}$ which indicated good toughness for this temperature. The fracture resistance did not appear to be a function of the specimen's location through the thickness of the plate for a given specimen orientation. In general, the fracture resistance of the weld and HAZ compared to the base metal was excellent. |  |                             |

DD FORM 1 JAN 64 1473

Unclassified

Security Classification

Unclassified

Security Classification

|     |  |        |    |        |    |        |    |
|-----|--|--------|----|--------|----|--------|----|
| 14. | KEY WORDS  | LINK A |    | LINK B |    | LINK C |    |
|     |  | ROLE   | WT | ROLE   | WT | ROLE   | WT |
|     | MITRON Welding Technique<br>Fracture Resistance<br>Fracture Toughness<br>Backup Flux |        |    |        |    |        |    |

### INSTRUCTIONS

1. **ORIGINATING ACTIVITY:** Enter the name and address of the contractor, subcontractor, grantee, Department of Defense activity or other organization (*corporate author*) issuing the report.
- 2a. **REPORT SECURITY CLASSIFICATION:** Enter the overall security classification of the report. Indicate whether "Restricted Data" is included. Marking is to be in accordance with appropriate security regulations.
- 2b. **GROUP:** Automatic downgrading is specified in DoD Directive 5200.10 and Armed Forces Industrial Manual. Enter the group number. Also, when applicable, show that optional markings have been used for Group 3 and Group 4 as authorized.
3. **REPORT TITLE:** Enter the complete report title in all capital letters. Titles in all cases should be unclassified. If a meaningful title cannot be selected without classification, show title classification in all capitals in parenthesis immediately following the title.
4. **DESCRIPTIVE NOTES:** If appropriate, enter the type of report, e.g., interim, progress, summary, annual, or final. Give the inclusive dates when a specific reporting period is covered.
5. **AUTHOR(S):** Enter the name(s) of author(s) as shown on or in the report. Enter last name, first name, middle initial. If military, show rank and branch of service. The name of the principal author is an absolute minimum requirement.
6. **REPORT DATE:** Enter the date of the report as day, month, year; or month, year. If more than one date appears on the report, use date of publication.
- 7a. **TOTAL NUMBER OF PAGES:** The total page count should follow normal pagination procedures, i.e., enter the number of pages containing information.
- 7b. **NUMBER OF REFERENCES:** Enter the total number of references cited in the report.
- 8a. **CONTRACT OR GRANT NUMBER:** If appropriate, enter the applicable number of the contract or grant under which the report was written.
- 8b, 8c, & 8d. **PROJECT NUMBER:** Enter the appropriate military department identification, such as project number, subproject number, system numbers, task number, etc.
- 9a. **ORIGINATOR'S REPORT NUMBER(S):** Enter the official report number by which the document will be identified and controlled by the originating activity. This number must be unique to this report.
- 9b. **OTHER REPORT NUMBER(S):** If the report has been assigned any other report numbers (*either by the originator or by the sponsor*), also enter this number(s).
10. **AVAILABILITY/LIMITATION NOTICES:** Enter any limitations on further dissemination of the report, other than those

imposed by security classification, using standard statements such as:

- (1) "Qualified requesters may obtain copies of this report from DDC."
- (2) "Foreign announcement and dissemination of this report by DDC is not authorized."
- (3) "U. S. Government agencies may obtain copies of this report directly from DDC. Other qualified DDC users shall request through \_\_\_\_\_."
- (4) "U. S. military agencies may obtain copies of this report directly from DDC. Other qualified users shall request through \_\_\_\_\_."
- (5) "All distribution of this report is controlled. Qualified DDC users shall request through \_\_\_\_\_."

If the report has been furnished to the Office of Technical Services, Department of Commerce, for sale to the public, indicate this fact and enter the price, if known.

11. **SUPPLEMENTARY NOTES:** Use for additional explanatory notes.
12. **SPONSORING MILITARY ACTIVITY:** Enter the name of the departmental project office or laboratory sponsoring (*paying for*) the research and development. Include address.
13. **ABSTRACT:** Enter an abstract giving a brief and factual summary of the document indicative of the report, even though it may also appear elsewhere in the body of the technical report. If additional space is required, a continuation sheet shall be attached.

It is highly desirable that the abstract of classified reports be unclassified. Each paragraph of the abstract shall end with an indication of the military security classification of the information in the paragraph, represented as (TS), (S), (C), or (U).

There is no limitation on the length of the abstract. However, the suggested length is from 150 to 225 words.

14. **KEY WORDS:** Key words are technically meaningful terms or short phrases that characterize a report and may be used as index entries for cataloging the report. Key words must be selected so that no security classification is required. Identifiers, such as equipment model designation, trade name, military project code name, geographic location, may be used as key words but will be followed by an indication of technical context. The assignment of links, rules, and weights is optional.

Unclassified

Security Classification